


ZAPP MEDICAL ALLOYS

DATA SHEET ERGSTE® 1.4123YN



CERTIFIED ACCORDING TO ISO 9001

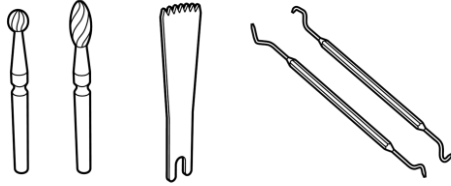

GRADE ERGSTE® 1.4123YN

Ergste® 1.4123YN is a nitrogen alloyed, martensitic, hardenable, stainless steel with extraordinary corrosion resistance and high hardness up to 57 HRC.

This material is preferred if special edge retention and abrasive resistance is required.

TYPICAL FIELDS OF APPLICATION

Medical instruments e. g.

- _ Cutting tools
- _ Drills
- _ Screwdrivers
- _ Chisels
- _ Saw blades

CORRESPONDING STANDARDS

1.4123 (X40CrMoVN16-2) acc. EN 10088-3
AISI 420Mod

WELDABILITY

Welding is possible without filler metal or with welding wire from 1.4016.

MAGNETISM

Ergste® 1.4123YN is magnetizable.

CORROSION RESISTANCE

Through the addition of nitrogen, Ergste® 1.4123YN shows an exceptional corrosion resistance.

CHEMICAL COMPOSITION

C	Si	Mn	Cr	Mo	N	P	S	V
0.37-0.45	≤ 0.60	≤ 0.60	15.00-16.50	1.50-1.90	0.16-0.25	≤ 0.02	≤ 0.005	0.20-0.40

PRODUCT CONDITIONS*

Bars, ground or ground and polished	Tensile [MPa]	700-900
-------------------------------------	---------------	---------

* Special conditions on request

PHYSICAL PROPERTIES

Modulus of Elasticity at 20 °C [GPa]	195
Specific Gravity [kg/dm³]	7.7
Thermal Conductivity 20°C [W/m*K]	24
Coefficient of Thermal Expansion [10 ⁻⁶ *K ⁻¹]	
20 - 100 °C	10.4
20 - 200 °C	10.5
20 - 300 °C	10.8
20 - 400 °C	11.1
20 - 500 °C	11.4
Specific Heat at 20 °C [kJ/kg*°C]	430
Electric Resistivity at 20 °C [Ω*mm²/m]	0.80

HEAT TREATMENT

SOFT ANNEALING

780 – 820 °C/ 7 h / Cooling: Furnace or air

STRESS RELIEF ANNEALING

150 – 220 °C/ 2 x 2 h/ Cooling: Air

HARDENING

1000 – 1050 °C/ 0,5 h/ Cooling: Oil

Hardening has to be conducted under nitrogen partial pressure to prevent reduction or increase of the nitrogen content.

TEMPERING

See tempering chart/ 2 x 2 h/ Cooling: Air

SUBZERO REFRIGERATION

-80 – -196 °C/ 1 h/ applied to eliminate remaining austenite at hardening temperatures of > 1010 °C.

SURFACE HARDENING

Ergste® 1.4123YN can be hardened by inductive heating. As initial condition, tempering to 35 – 40 HRC is recommended.

MACHINING

Ergste® 1.4123YN is characterized by an outstanding machinability.


HOT WORKING

Forging at 1220 - 1000 °C.

POLISHABILITY

Ergste® 1.4123YN shows excellent abilities for grinding and polishing.

TEMPERING CHART (HARDENING WITH SUBZERO REFRIGERATION)

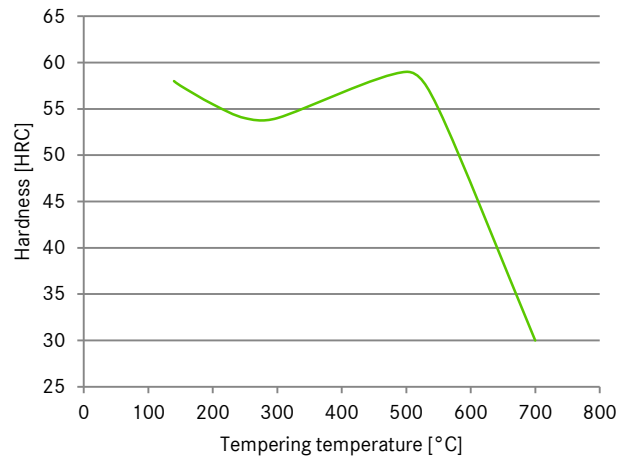

ZAPP MEDICAL ALLOYS

Zapp Medical Alloys GmbH
Letmather Straße 69
58239 Schwerte
P.O. Box 17 20
58212 Schwerte
Phone +49 2304 79-540
Fax +49 2304 79-482
medicalalloys@zapp.com

www.zapp.com

Further information regarding our products and locations are available in our image brochure and under www.zapp.com

The illustrations, drawings, dimensional and weight data and other information included in this data sheet are intended only for the purposes of describing our products and represent non-binding average values. They do not constitute quality data, nor can they be used as the basis for any guarantee of quality or durability. The applications presented serve only as illustrations and can be construed neither as quality data nor as a guarantee in relation to the suitability of the material. This cannot substitute for comprehensive consultation on the selection of our products and on their use in a specific application. The brochure is not subject to change control.

Last revision: October 2011